

# Mechanical and superconducting properties of nanosize MgO added dip-coated $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_8$ superconducting tape

Nasri A. Hamid\*, Mohd Yusri Abd Rahman, Noor Fairuz Shamsudin

Department of Engineering Sciences & Mathematics, College of Engineering, Universiti Tenaga Nasional, Kajang, Selangor, Malaysia; \*corresponding author: [nasri@uniten.edu.my](mailto:nasri@uniten.edu.my)

Received 2 February 2011; revised 10 March 2011; accepted 20 March 2011.

## ABSTRACT

In this work, 3% to 8% (in weight) of nanosize MgO particles was added to  $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_8$  (Bi-2212) high-temperature superconductor to fabricate Bi-2212 superconducting material with superior mechanical properties. The mechanical strength of the samples was studied by conducting the compression test at room temperature, and the addition of 5% nanosize MgO particles produced the highest strength when compared with other samples. The sample with 5% MgO addition also exhibited superior superconducting properties. The Bi-2212 powder with 5% nanosize MgO addition was used to fabricate Bi-2212 tapes through the dip-coating-then-stacking method. The fully processed tapes were investigated via dc electrical resistance measurements, XRD patterns, SEM micrographs, transport critical current density and tensile tests. The tensile tests were conducted at room and cryogenic (77 K) temperatures. Results of tensile tests and Young's modulus for the tapes showed that the Bi-2212 tapes with nanosize MgO addition recorded better mechanical property compared to the non-added samples both at room and cryogenic temperatures. The double-core tape with 5% MgO addition recorded the highest failure point at 160 MPa. In addition to the strengthening effect that was observed in the nanosize MgO added Bi-2212 superconductor tapes, the superconducting properties remained intact in the tapes.

**Keywords:** Bi-2212 Superconductor; Electrical Properties; Mechanical Properties; High Current Density; Cryogenic Temperature

## 1. INTRODUCTION

For practical applications of high-temperature superconductor materials in power engineering, where thermo-mechanical and electromagnetically induced stresses are expected to occur, the high-temperature superconductor materials need to have excellent superconducting properties and higher mechanical strength. Bismuth based high-temperature superconductors such as  $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_8$  (Bi-2212) is one of the most promising materials due to its high critical current density, rapid phase formation and phase stability. Nevertheless the Bi-2212 superconductor, like other Bi-based high-temperature superconductors is generally has poor mechanical properties such as low stiffness, strength and toughness despite their excellent superconducting properties [1-4]. Low strength and low irreversible strain are among the factors that hindered the application of Bi-2212 superconductor in power industry. MgO fibers have been used to reinforce Bi-2212 superconductor and are able to improve the mechanical properties of the compounds [4,5]. Furthermore, the addition of nanosize MgO particles has shown to be an effective pinning center for Bi-2212/MgO compounds and samples with nanocrystalline microstructures are found to exhibit better plasticity under stress compared with samples of larger grains [6-10].

In the literature, there is no specific report that focuses on the mechanical strength of single-core and double-core dip-coated Bi-2212 superconducting tapes with nanosize MgO addition both at room and cryogenic temperatures. In the present work, we report our study on the mechanical and superconducting properties of such tapes at room and cryogenic temperatures and the data from this study is important in assessing the performance of the tapes especially at cryogenic temperature. Throughout this study, the tapes were fabricated using the dip-coating-then-stacking (DIS) method [11].

## 2. EXPERIMENTAL PROCEDURES

The Bi<sub>2</sub>Sr<sub>2</sub>CaCu<sub>2</sub>O<sub>8</sub> (Bi-2212) with nanosize MgO addition tapes were prepared through the DIS method. The silver foil that was used in the fabrication of the tapes was product of Alfa Aesar with 0.1 mm in thickness and 99.998% purity. In the process, slurry with an optimum composition was prepared before employing the dip-coated process. In preparation of the slurry, organic solution comprises of Span 85 or sorbitane trioleate (C<sub>60</sub>H<sub>108</sub>O<sub>8</sub>), 1,3-propanediol (C<sub>3</sub>H<sub>8</sub>O<sub>2</sub>), polyvinyl butyral and trichloroethylen (C<sub>2</sub>HCl<sub>3</sub>) were used. The Bi-2212 powder (with and without nanosize MgO addition) was then added with the solution in the ratio as shown in **Table 1**.

The slurry was stirred for 24 hours to obtain a homogeneous solution before coating. The coated tape was then heated at temperature of 80°C for 48 hours to remove any oxide layers before further heating at 500°C in flowing oxygen for one hour to remove the organic materials. After heating, the tape was stacked and consequently rolled to increase the packing density of the oxide core before it is subjected to partial melt process. During the heat treatment process, the samples were heated up from room temperature for 2.88 hours until it reached the partial melt temperature at 865°C. The temperature was hold for 6 minutes and then cooled down from 865°C to 830°C in 3.5 hours. They were annealed at 830°C for 48 hours and then cooled down to room temperature in 2.77 hours. Partial melt process was employed to overcome the problem of weak-link within the Bi-2212 superconducting grains.

The fully processed tapes were characterized through dc electrical resistance measurements, XRD patterns, SEM micrographs, and transport critical current density,  $J_c$ . In the dc electrical resistance measurements,  $T_{c, \text{onset}}$  corresponds to the transition onset temperature which is the point on the R(T) curve where the resistance starts decreasing dramatically, and  $T_{c, \text{zero}}$  corresponds to transition zero temperature where the resistance is zero. The XRD patterns were recorded on a Siemen D5000 diffractometer using Cu K $\alpha$  radiation. The SEM analysis of the longitudinal and broad-face cross sectional of the tapes were conducted using the Philips XL30 environmental scanning electron microscope with EDX analysis. The transport critical current ( $I_c$ ) of short samples was

**Table 1.** Formulation of slurry used to fabricate dip-coated tapes.


Component	Material	Fractions (Weight %)
Oxide powder	Bi-2212/ nanosize MgO	22
Solvent	Trichloroethylene	68
Binder	Polyvinyl butyral	6
spersant	Sorbitant triolate	4

measured in a cryostat at 77 K and zero electric field using the four-probe method with a 1  $\mu\text{V}/\text{cm}$  criterion. The transport critical current density ( $J_c$ ) was calculated by dividing  $I_c$  with the cross-sectional area of the superconducting core. The mechanical properties of the tapes were studied using tensile tests that were conducted at room and cryogenic (77 K) temperatures. The tests were conducted using the Instron Material Testing System model 5567. The slope of the stress-strain curve in the elastic region represents the stiffness of the material. In a tensile test, a sample is extended at a constant rate and the maximum load is measured. The Young's modulus was estimated from the linear part of the stress-strain curve.

## 3. RESULTS AND DISCUSSIONS

**Figure 1** shows a typical resistivity curve of the tape samples. The curve shows a metallic behavior due to the silver tape until the onset temperature where the resistance propitiously dropped to zero. The sharp drop of the curve indicates high purity of Bi-2212 phase in the superconducting core of the tape.

From our observation, the XRD patterns for both the non-added and nanosize MgO added Bi-2212 tapes show a well defined peaks all of which could be indexed on the basis of a Bi-2212 structure. The (115) peak, which is the characteristic of the Bi-2212 phase, can be observed clearly in all the samples. Patterns of the nanosize MgO added tape samples show a more distinct and sharp Bi-2212 phase peaks, indicating a highly crystalline and well textured microstructure. A few peaks which correspond to secondary phases such as Bi-2201 phase and other impurities could also be observed. Those unidentified peaks are probably due to inappropriate heat treatment during the sintering process which resulted in uni-

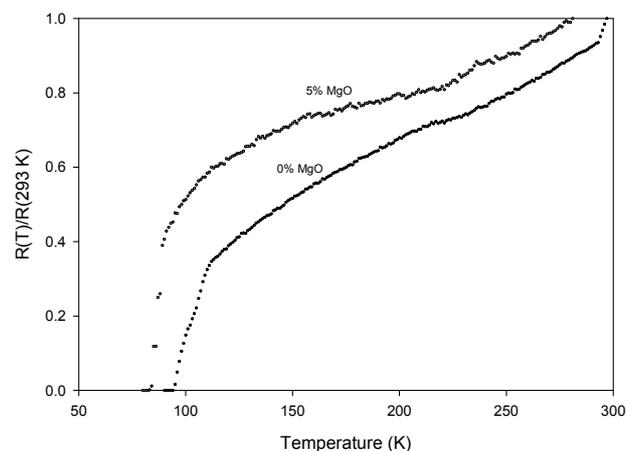


**Figure 1.** Temperature dependence of resistance of dip-coated Bi-2212 superconducting tapes (with and without nanosize MgO addition).

identified secondary phases.

**Figure 2** shows a typical SEM micrograph of the longitudinal cross-sectional of the dip-coated Bi-2212 superconducting tape with nanosize MgO addition. The micrograph exhibits a well aligned microstructure of the Bi-2212 superconducting core with closely connected grain boundaries.

**Table 2** shows the critical current density,  $J_c$ , zero transition temperature,  $T_{c\ zero}$  and onset transition temperature,  $T_{c\ onset}$  of the tapes. For both the single-core and double-core tapes, there is enhancement in the  $J_c$  after addition of nanosize MgO. From the observation of XRD patterns and SEM micrograph, the enhancement is most likely due to better texturing and well connected grain boundaries of the superconducting core. The  $J_c$  of the tapes is very much dependent on microstructural features such as phase purity, grain alignment and grain boundaries.


Mechanical properties such as stiffness, strength and toughness are important parameters to indicate the versatility of superconducting tapes [12,13]. Those properties at room temperature are able to predict such behaviors at cryogenic temperature. **Figure 3** shows a typical stress-strain curve for a double-core dip-coated Bi-2212 superconducting tape with nanosize MgO added both at room and cryogenic temperatures. The non-linear curve at the initial load is due to low rigidity in which the tape

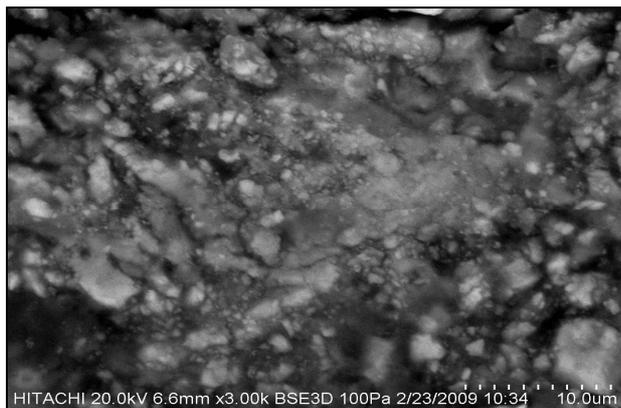

**Figure 2.** Typical SEM micrograph of the longitudinal cross-sectional of the dip-coated Bi-2212 superconducting tape.

**Table 2.** The critical current density,  $J_c$  and transition temperature,  $T_c$  of the dip-coated Bi-2212 superconducting tape.

Nanosize MgO Addition	$J_c$ (A/cm <sup>2</sup> ) $\pm$ 10	$T_{c\ zero}$ (K)	$T_{c\ onset}$ (K)
0% (single-core)	1800	94	101
5% (single-core)	2400	82	95
0% (double-core)	1900	82	88
5% (double-core)	2300	89	98

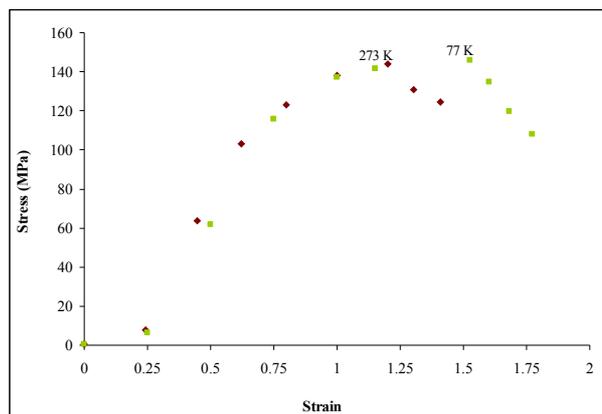

**Figure 3.** The stress-strain curve for a double-core dip-coated Bi-2212 superconducting tape with nanosize MgO addition at room temperature ( $\blacklozenge$ ) and 77 K ( $\blacksquare$ ).

sample was not completely attached to the tester. As the load increases, a more linear relationship is observed until deformation and eventually to the failure point. From our results, a more distinct linear curve was observed in the MgO added samples before deformation both at room and cryogenic temperatures. The presence of MgO particles resulted in different mechanical behavior between the MgO added and non-added tapes.

**Table 3** shows the tensile test measurements for the single-core and double-core tapes both at cryogenic and room temperatures. At cryogenic temperature, all the tapes exhibit higher strength when compared to room temperature. The double-core tape added with nanosize MgO recorded the highest strength at about 160 MPa. In addition, the Young's modulus for each tape can be estimated based on the linear part of each curve. In contrast to the tapes' strength, the Young's modulus of the MgO added tape slightly decreased at cryogenic temperature. This is mostly due to lower stiffness of the tape initiated by microcracks that developed between the MgO particles and the Bi-2212 superconductor matrix during cooling to cryogenic temperature [14]. Nevertheless, the Young's modulus is still higher compared to the non-added tape sample. As such, the Bi-2212 superconducting tapes with nanosize MgO addition show better resilience at cryogenic temperature.

**Table 3.** The tensile test results for double-core and single-core tapes both at room and cryogenic temperatures.

Nanosize MgO Addition	Max. Strength at 77 K (MPa) $\pm$ 0.01	Max. Strength at Room Temperature (MPa) $\pm$ 0.01
0% (single-core)	144.91	117.59
5% (single-core)	146.22	144.83
0% (double-core)	151.01	116.65
5% (double-core)	159.81	146.68

## 4. CONCLUSIONS

We have successfully fabricated nanosize MgO added Ag-sheathed Bi-2212 superconducting tapes using the dip-coating-then-stacking (DIS) method. The samples were subjected to a combination of partial melt and slow cooling during heat treatment and annealing processes. The addition of nanosize MgO in both single-core and double-core tape samples enhanced the  $J_c$  and this was attributed to the presence of MgO that acted as pinning centers. The double-core tape with 5% nanosize MgO addition recorded the highest strength. As such, the addition of nanosize MgO contributed to the improvement of the mechanical properties of the tapes without degrading their superconducting properties.

## 5. ACKNOWLEDGEMENTS

This project is supported by the Ministry of Science, Technology and Innovation, Malaysia through eScience fund project no. 03-02-03-SF0034.

## REFERENCES

- [1] Yuan, Y.S., Wong, M.S. and Wang, S.S. (1996) solid-state processing and phase development of bulk(MgO) w/BPSCCO high-temperature superconducting composite. *Journal of Materials Research*, **11**, 8-17.
- [2] Nomura, K., Sasaoka, T., Sato, J., Kuma, S., Kumakura, H., Togano, K. and Tomita, N. (1994) Influence of Ag - Au and Ag - Cu alloys on  $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_x$  superconductor. *Applied Physics Letters*, **64**, 112-114. [doi:10.1063/1.110895](https://doi.org/10.1063/1.110895)
- [3] Li, T.W., Drost, R.J., Kes, P.H., Træholt, H.W., Zandbergen, H.W., Hien, N.T., Menovsky, A.A. and Franse, J.J.M. (1997) Enhanced flux pinning in Bi-2212 single crystals by planar defects introduced via Ti-substitution. *Physica C*, **274**, 197-203. [doi:10.1016/S0921-4534\(96\)00699-5](https://doi.org/10.1016/S0921-4534(96)00699-5)
- [4] Chen, Y. J., Li, J. B., Han, Y. S., Yang, X. Z. and Dai, J. H. (2003) Fabrication of decorated MgO crystalline fibers. *Materials Research Bulletin*, **38**, 445-452.
- [5] Chen, M., Glowacka, D.M., Soylyu, B., Watson, D.R., Christiansen, J.K.S., Baranowski, R.P., Glowacki, B.A. and Evetts, J.E. (1995) Texture and critical current anisotropy in composite reaction textured MgO whisker/Bi-2212 multilayer structures. *IEEE Transactions on Applied Superconductivity*, **5**, 1467-1470. [doi:10.1109/77.402843](https://doi.org/10.1109/77.402843)
- [6] Watson, D.R., Chen, M. and Evetts, J.E. (1995) The fabrication of composite reaction textured  $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+\delta}$  superconductors. *Superconductor Science and Technology*, **8**, 311.
- [7] Wei, W., Schwartz, J., Goretta, K.C., Balachandran, U. and Bhargava, A. (1998) Effects of nanosize MgO additions to bulk  $\text{Bi}_{2.1}\text{Sr}_{1.7}\text{CaCu}_2\text{O}_x$ . *Physica C*, **298**, 279-288. [doi:10.1016/S0921-4534\(97\)01889-3](https://doi.org/10.1016/S0921-4534(97)01889-3)
- [8] Ni, B., Tomishige, Y., Xiong, J. and Zhao, Z.X. (1999) Flux pinning due to MgO particle additions in partial-melt processed Bi-2212 bulk. *IEEE Transactions on Applied Superconductivity*, **9**, 2347-2350. [doi:10.1109/77.784942](https://doi.org/10.1109/77.784942)
- [9] Agranovski, I.E., Ilyushechkin, A.Y., Altman, I.S., Bostrom, T.E. and Choi, M. (2006) Methods of introduction of MgO nanoparticles into Bi-2212/Ag tapes. *Physica C*, **434**, 115-120. [doi:10.1016/j.physc.2005.12.005](https://doi.org/10.1016/j.physc.2005.12.005)
- [10] Müller, C., Majewski, P., Thürn, G. and Aldinger, F. (1997) Processing effects on mechanical and superconducting properties of Bi2201 and Bi2212 glass ceramics. *Physica C: Superconductivity*, **275**, 337-345. [doi:10.1016/S0921-4534\(97\)00026-9](https://doi.org/10.1016/S0921-4534(97)00026-9)
- [11] Sung, Y.S., Kumakura H. and Togano, K. (2000) Dip-coated multi-core  $(\text{Bi,Pb})_2\text{Sr}_2\text{Ca}_2\text{Cu}_3\text{O}_x$  tape process—an alternative way of fabricating multi-core  $(\text{Bi,Pb})_2\text{Sr}_2\text{Ca}_2\text{Cu}_3\text{O}_x$  tape conductors. *Physica C: Superconductivity*, **331**, 171-177. [doi:10.1016/S0921-4534\(00\)00002-2](https://doi.org/10.1016/S0921-4534(00)00002-2)
- [12] Tamura, H., Mito, T., Iwamoto, A., Yamada, Y. and Tachikawa, K. (2002) Mechanical properties and reinforcement of Bi-2212 tubular bulk superconductor for current lead. *IEEE Transactions on Applied Superconductivity*, **12**, 1319. [doi:10.1109/TASC.2002.1018645](https://doi.org/10.1109/TASC.2002.1018645)
- [13] Miyase, A., Yuan, Y.S., Wong, M.S., Schön, J. and Wang, S.S. (1995) Cryogenic- and room-temperature mechanical behaviour of an  $\text{Al}_2\text{O}_3$ -fibre-reinforced high-temperature superconducting  $(\text{Bi,Pb})_2\text{Sr}_2\text{Ca}_2\text{Cu}_3\text{O}_x$  ceramic matrix composite. *Superconductor Science and Technology*, **8**, 626. [doi:10.1088/0953-2048/8/8/005](https://doi.org/10.1088/0953-2048/8/8/005)
- [14] Salib, S., Mironova, M., Vipulanandan, C. and Salama, K. (1996) Mechanical properties and TEM studies on BPSCCO-2223-Ag composite tapes. *Superconductor Science and Technology*, **9**, 1071. [doi:10.1088/0953-2048/9/12/009](https://doi.org/10.1088/0953-2048/9/12/009)